



Written on 04 July 2024



4 minutes of reading



News

Fundamental Research

Physical chemistry

Complex fluids, colloids and condensed matter

Surface, interface and materials science

Electrochemistry and corrosion

Carbon steel is a construction material that is widely used in industry, due to its excellent cost/performance ratio. Nevertheless, in certain applications, it can come into contact with an aggressive environment, such as aqueous environments that have been acidified by the presence of CO_2 , leading to corrosion-induced deterioration. In order to gain a better

understanding and improve the protection of carbon steels in environments of this type, corrosion teams from IFPEN, INSA-Lyon's Mateis Laboratory and the University of Leeds' Institute of Functional Surfaces (IFS) have pooled their expertise to conduct joint research. The research is aimed at controlling the performance of the “pseudo passive” surfaces observed on these steels, developing characterization methodologies to study the protection mechanisms involved.

Corrosion resistance, an Achilles' heel for different usages related to the ecological transition

The transition to a low-carbon economy requires new technologies. Some of these, including CCUS (Carbon Capture Utilization and Storage) and biofuel synthesis, involve **aqueous effluents containing CO₂ in solution**. These environments may be a source of corrosion affecting the equipment employed, particularly if it is made of carbon steel. **Carbon steel** is associated with numerous advantages due to its low cost, availability, and recyclability, as well as its mechanical and assembly (machining, welding) properties. However, its corrosion resistance remains a weak point. Nevertheless, in certain conditions, **its surface may be protected by the formation of a “pseudo passive” layer**. A layer of iron oxide or carbonate is formed on the surface, which can potentially be reinforced by the incorporation of other metallic elements.

Evaluation of the physicochemical conditions close to the corroding surface

In order to better characterize the aqueous environment in the corrosion zone, a specific set-up (figure 1) was developed to evaluate the local pH in the closed vicinity of a sample immersed in an aqueous medium containing CO₂. The set-up takes the form of a carbon steel grid.

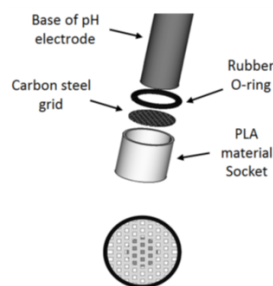


Figure 1: pH electrode diagram [1]

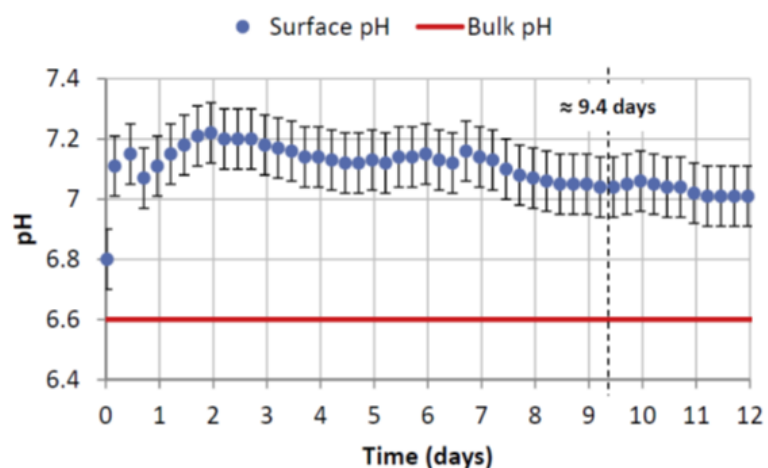


Figure 2: Surface pH measurement conducted for a pH of 6.6 measured in a full bath (a long way from the sample surface) over a test period of 12 days at 80°C at 0.54 bar of CO₂ [1]

As indicated in figure 2, at the interface where corrosion takes place, the pH measured is less acidic by around 0.4 units of pH compared to the pH of the solution a long way from the interface [1]. **This local condition is favorable to the formation of a pseudo passive layer.**

Carbon steel “pseudo passivity” protection mechanisms

Electrochemical measurements have confirmed that **the pseudo-passive state is characterized by a change in open circuit potential and a significant reduction in the corrosion rate.** This can be observed in figure 3 with, after 10 days, a corrosion rate that has become so low (less than 0.02 mm/year) that it enables long-term use of carbon steel.

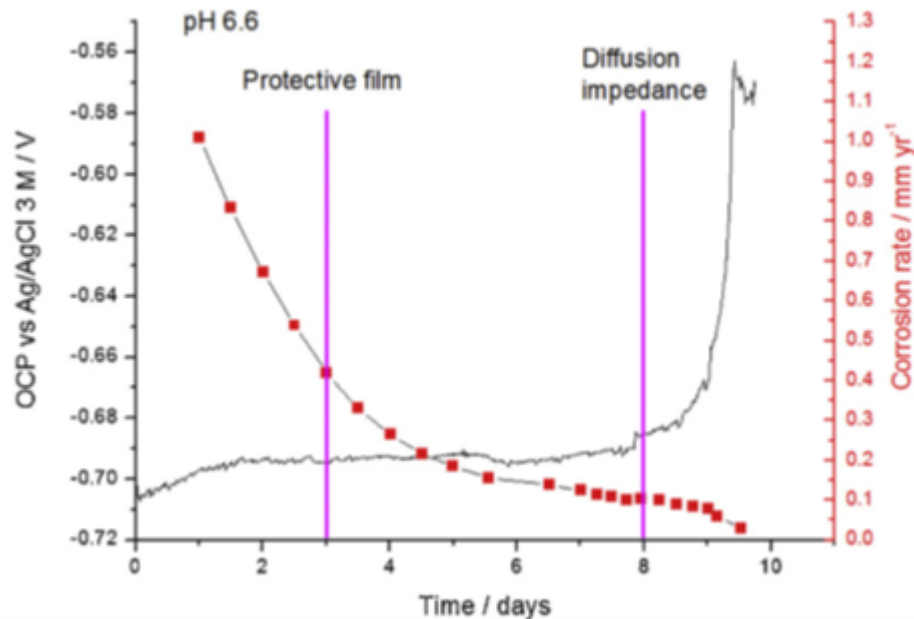


Figure 3: evolution of Open Circuit Potential and corrosion rate as a function of immersion time for a bulk bath pH of 6.6 (interfacial pH of 7) at 80°C and 0.54 bar of CO₂ [2]

For a sample exposed to 80°C and a pH of 6.6, surface analyses identified traces of a magnetite phase (Fe₃O₄) at certain places, beneath a more dominant iron carbonate (FeCO₃) film (figure 4). In addition, over the course of time, **the corrosion layer acquires a very low porosity**, resulting in the formation of a “diffusion barrier”. This is indicated in figure 3 by **a significant increase in the open circuit potential (OCP)**, which is considered to be a key corrosion protection indicator [2].

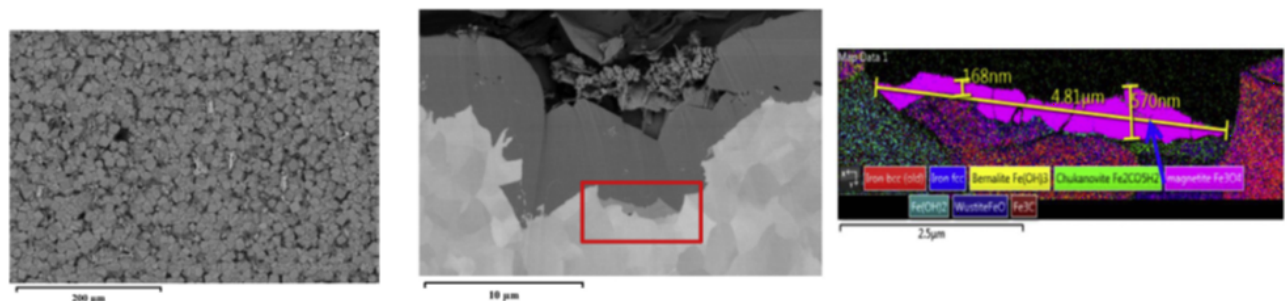


Figure 4: SEM image of the surface (left) - SEM image of a cross-section of the pseudo-passive layer (center) - EBSD map showing the presence of magnetite at the steel/pseudo-

passive layer interface (right) after 12 days' immersion at a bulk-bath pH of 6.6 (interfacial pH of 7) at 80°C and 0.54 bar of CO₂ [2]

¹ Electron Backscatter Diffraction

In situ corrosion monitoring using synchrotron radiation

In situ synchrotron X-ray diffraction (SR-XRD) was also used to monitor **the evolution of corrosion products on X65 carbon steel in an aqueous environment containing CO₂** (following exposure to 80°C, pH 6.3–7.3). A custom-designed flow cell was built for the purpose, enabling real-time monitoring of concomitant changes in electrochemical behavior and corrosion product growth [3]. Measurements were carried out both during **natural "pseudo-passivation"** stages and under potentiodynamic polarization conditions, to investigate electrochemical mechanisms in the cathodic and anodic domains (Figure 5).

² i.e., varying the sample potential

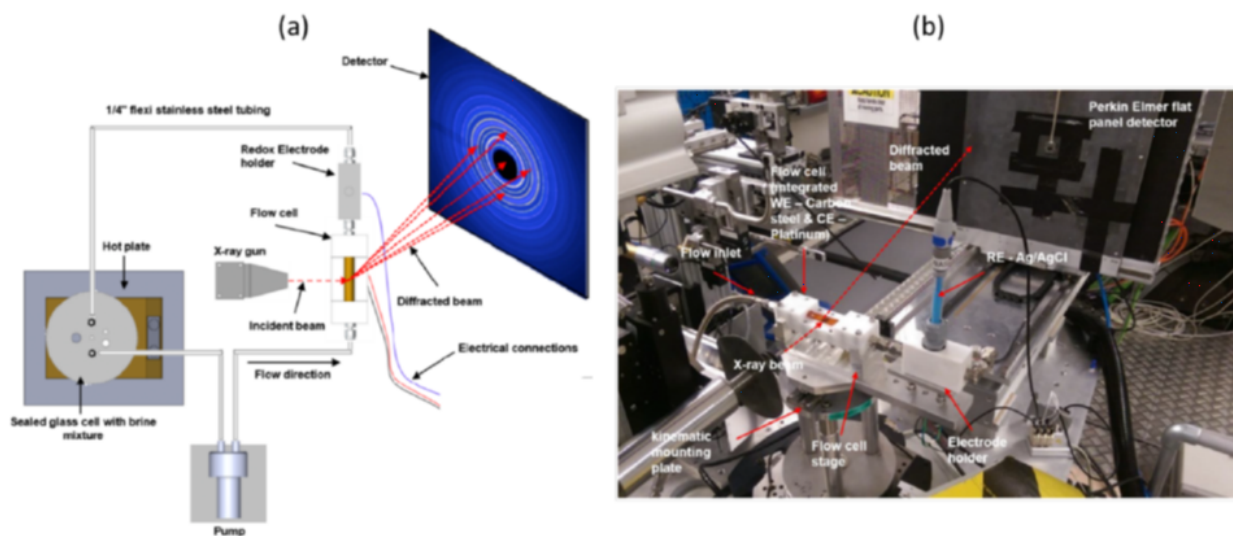


Figure 5:(a) Illustration and(b) configuration of the flow cell used on the Diamond Light Source beamline (Oxford) [3]

The protectivity (reflected by a nobler open circuit potential) observed during "pseudo-passivation" is strongly linked to the accumulation of iron carbonate (FeCO_3) on the steel surface (figure 6). The chukanovite $\text{Fe}_2(\text{OH})_2\text{CO}_3$ was only detected at higher anodic potentials (associated with a rapid steel dissolution rate), outside the pseudo passive protection domain (figure 7): this phase thus appears to be associated with the active dissolution of carbon steel [3].

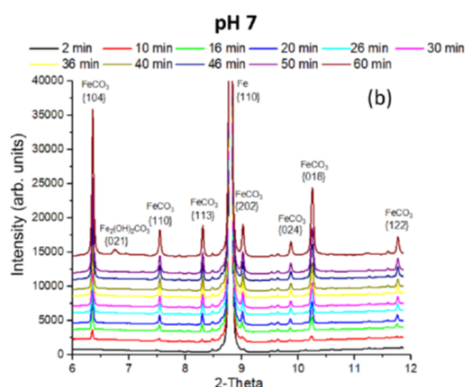


Figure 6: In situ XRD analysis of an X65 carbon steel coupon at 80°C at 0.54 bar of CO₂, flowing at a velocity of 0.1 m/s through a flow cell at pH 7. Individual diffraction peaks evolving with time over the course of a test duration of around 1 hour [3].

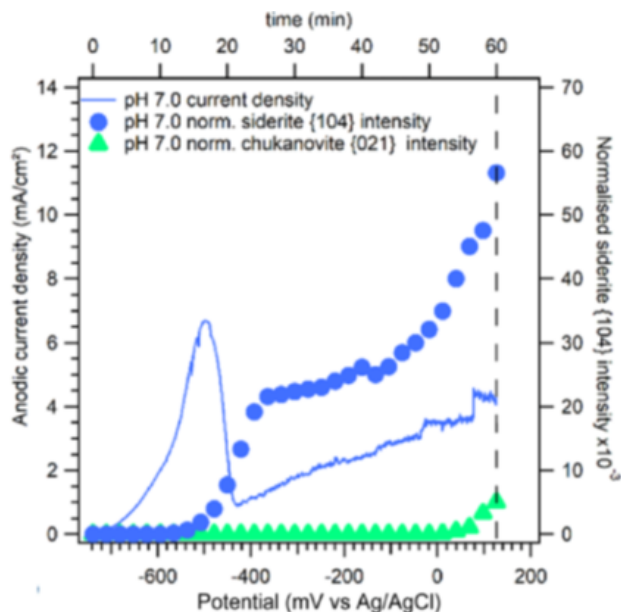


Figure 7: Normalized FeCO₃ (104) and Fe₂(OH)₂CO₃ (021) lattice plane intensity during potentiodynamic polarization in the anodic domain of the X65 carbon steel coupon in an 80 °C and 3.5 wt% NaCl solution saturated with CO₂ at 0.54 bar pCO₂, flowing at a velocity of 0.1 m/s through the flow cell at pH 7 [3].

Conclusion

This collaborative fundamental research led to a better understanding of the protection mechanisms association with the “pseudo passivation” of carbon steel in aqueous environments containing carbon dioxide. It also demonstrates the interest of the methodologies implemented, in particular **in situ electrochemistry in a synchrotron**. These methodologies were also used to study the reinforcement of protection by the incorporation of magnetite in the pseudo passive layer [4-5], as well as the impact of contaminants, such as oxygen, on the duration of pseudo passivation. [6-7]

References:

- [1] R. de Motte, R. Mingant, J. Kittel, F. Ropital, P. Combrade, S. Necib, V. Deydier, D. Crusset, **Near Surface pH Measurements in Aqueous CO₂ Corrosion**, *Electrochimica Acta*, 2018, 290, 605-615
>> DOI : <https://doi.org/10.1016/j.electacta.2018.09.117>
- [2] R.de Motte, E. Basilico, R. Mingant , J. Kittel, F. Ropital, P. Combrade, , S. Neicib,, V. Deydier, D. Crusset,, S. Marcelin, **A study by electrochemical impedance spectroscopy and surface analysis**

of corrosion product layers formed during CO₂ corrosion of low alloy steel, Corrosion Science, 2020, Volume 172 1 August Article 108666

>> DOI : <https://doi.org/10.1016/j.corsci.2020.108666>

[3] J. Owen; D. Burkle, E. Basilico, S. Marcelin, F. Ropital; G.R. Joshi; J. Kittel; A. Kleppe, R.C. Woollam, R. Barker, **In situ SR-XRD analysis of corrosion product formation during ‘pseudo-passivation’ of carbon steel in CO₂-containing aqueous environments**, Corrosion Science, 225 (2023) 111598,

>> DOI : <https://doi.org/10.1016/j.corsci.2023.111598>

[4] J. Owen, R. Barker, F. Ropital, G. R. Joshi, J. Kittel, R. Jacklin, D. Burkle, E. Straume, S. N. Karlsdóttir, **Modified magnetite surface layers on carbon steel in aqueous CO₂ environments**, NACE/AMPP 2023 Conference paper 19127

[5] J. Owen; F. Ropital; G.R. Joshi; J. Kittel; R. Barker, **Galvanic effects induced by siderite and cementite surface layers on carbon steel in aqueous CO₂ environments**, Corrosion Science, 2022-10,

>> DOI : <https://doi.org/10.1016/j.corsci.2022.110762>

[6] E. Basilico, S. Marcelin, R. Mingant , J. Kittel, M. Fregonese, J. Owens, R. Barker, A. Neville, F. Ropital, **Effect of O₂ contamination on carbon steel pseudo-passive scales in CO₂ aqueous solutions**, Corrosion Science, 2022, Vol 205, Article 110388

>> DOI : <https://doi.org/10.1016/j.corsci.2022.110388>

[7] E. Basilico, S. Marcelin, R. Mingant , J. Kittel, M. Fregonese, F. Ropital, **The effect of chemical species on the electrochemical reactions and corrosion product layer of carbon steel in CO₂ aqueous environment: A review**, Materials and Corrosion, 2021, 1, 16

>> DOI : <https://doi.org/10.1002/maco.202012118>

Scientific contacts: François Ropital, Jean Kittel, gaurav.joshi@ifpen.fr

The research presented was primarily conducted within the framework of the post-doctoral research by Rehan de Motte, the PhD thesis of Edoardo Basilico and the scientific visit at IFPEN of Joshua Owens. We extend our sincerest thanks to them.

YOU MAY ALSO BE INTERESTED IN

[Carbon steel in self-defense mode against corrosion](#)

The French Corrosion Institute and IFPEN sign a framework partnership agreement relating to the energy transition

The French Corrosion Institute and IFPEN sign a framework partnership agreement relating to the energy transition

Understanding and improving the protection of carbon steels in aqueous environments containing CO₂

04 July 2024

Link to the web page :